

Original Article | ISSN (0): 2582-631X

DOI: 10.47857/irjms.2024.v05i04.01854

# Optimization of Physical Parameters of Fermentation Medium for Biosynthesis of Alginate by *A. vinelandii* Using Molasses as 'C' Source

Zarina Shaikh1\*, Mohd Shakir2

<sup>1</sup>Dr. Rafiq Zakaria Centre for Higher Learning and Advanced Research, Aurangabad, Maharashtra, India, <sup>2</sup>Mrs. KSK College of Arts, Science and Commerce, Beed, Maharashtra, India. \*Corresponding Author's Email: skzarina1@gmail.com

#### **Abstract**

Biopolymer have varied industrial applications. Alginate is one such polymer conventionally extracted from brown algae of marine waters having versatile applications. Due to its increased market demand alternative options are being investigated for its synthesis from microbes. The present study focuses on the optimization of various physical parameters at flask level. Fermentation medium consisted of pre-treated sugar cane molasses (2%) as carbon source and peptone as nitrogen source (0.5 g). The optimized parameters were found to be, temperature as  $30^{\circ}$ C, pH 7.0, incubation period 84 hours, agitation rate 150 rpm, inoculum age 36 hours and inoculum level 5%. Under optimized parameters the significant (P<0.05) alginate yield was found to be 5.71 g/L (PS) and 6.28 g/L (MS) with the corresponding dry cell mass (DM) as 6.28 g/L (PS) and 6.92 g/L (MS). The plate assay of the alginate lyase activity indicated that the improved strain has less activity (11 mm) as compared to the parent strain (14 mm). Alginate lyases influence the yield and the molecular weight of the product. Hence the zone of hydrolysis on the plates correlates with the maximum yield obtained. HPLC chromatogram indicated the peak of purified alginate with retention time of 3.332 minutes with purity of 81.22 %.

**Keywords:** Alginate, Alginate Lyase, *Azotobacter vinelandii*, Molasses.

### Introduction

Alginates is one of the natural polysaccharides obtained from seaweeds and can also be biosynthesized by using bacteria. biosynthesis Unlike brown algae the from *Azotobacter* species have several advantages (1). Bacterial alginate differ in physicochemical properties they possess 0-acetylation at C<sub>2</sub> and C<sub>3</sub> positions in mannuronic acid residues (2). This affects its viscosity, interaction with calcium ions and a reaction of mannuronan epimerase, and mannuronan lyase (3, 4). Bacterial synthesis under controlled laboratory conditions is advantageous for obtaining the polymer in a variety of physicochemical properties (5, 6). Alginate biosynthesis with Azotobacter genus is preferable as it is a non-pathogen (7). Alginates are used as stabilizers, thickeners, gelling or film-forming agent for various applications in the food, medical pharmaceutical industries (8-10)environmental.

They show excellent biocompatibility and biodegradability. Algal alginates show low

consistency which limits their role in advanced biomedical applications. Microbial production is lucrative due to its potential for synthesizing customized alginate molecules with stable characteristics. Economic concern is the major limiting factor for the commercialization of microbial alginates. However, carbon-rich wastes from dairy, sugar and biodiesel industries may serve as substitutes for pure carbon sources thus reducing the substrate costs. Fermentation parameter control may improve the production efficiency (11). In the present research work optimization of major physical parameters and some biological parameters (inoculum age, inoculum %) has been done to improve the yield using pre-treated molasses as a source of carbon.

# Materials and Methods Culture Isolation and Preservation

Azotobacter vinelandii (Parent Strain) was isolated from the soil. The isolate was maintained as pure culture on Burk's Nitrogen free agar

This is an Open Access article distributed under the terms of the Creative Commons Attribution CC BY license (http://creativecommons.org/licenses/by/4.0/), which permits unrestricted reuse, distribution, and reproduction in any medium, provided the original work is properly cited.

(Received 31st July 2024; Accepted 25th October 2024; Published 30th October 2024)

medium slants (12). Burk's medium in g/l ( $K_2HPO_4$  0.8 g,  $KH_2PO_4$  0.2 g,  $MgSO_4.7H_2O$  0.2g, NaCl 0.2g,  $CaSO_4$  0.1g, Fe-Mo Mixture – 0.1 ml, Sucrose 20.0g,  $H_3BO_3$  100µg,  $ZnSO_4.7H_2O$  100µg,  $MnSO_4.4H_2O$  10.0µg,  $CuSO_4.5H_2O$  3µg, KI 1.0µg, D/W 100 ml, PI – 7.3); (Fe-Mo Mixture preparation -  $FeCl_3.6H_2O$  – 1.45g,  $Na_2MoO_4.2H_2O$  – 0.253g; D/W – 100 ml) incorporated with 0.5 g peptone was used for inoculum development and fermentation.

# **Optimization of Physical Parameters for Alginate Production**

Preparation of inoculum - Inoculation of loop full of bacterial culture in 25 mL of Nitrogen-free sucrose medium contained in 250 mL conical flask with incubation on rotary shaker at 30° C. Twentyfour hour's old culture was used as inoculum with culture density set as 0.6 at 600 nm (12). Preoptimized carbon and nitrogen sources i.e. molasses [2%] and peptone [0.5%] were added in the Burk's medium. Optimization of parameters was done in conical flasks of 250 mL (Erlenmeyer flask) having 50 mL of total fermentation medium (triplicates). Parameters included various time intervals [24, 48, 72, 96, 108 hours], percentages of inoculum [1-10%] (13), inoculum age [24, 36, 48, 60 hours], pH values [5, 6, 7, 8, 9], degree of temperature [25°C, 30°C, 35°C, 40°C, 45°C] and agitation rate [0, 100, 150, 200 rpm] were tested to achieve maximum yield of alginate.

# **Alginate Lyase Plate Assay**

Crude clear supernatant was obtained after centrifugation of Burk's culture medium at 8000 rpm for 20 minutes, it was used as the source of alginate lyase. Plate assay was performed using plates containing 1% agarose and 0.1% commercially available sodium alginate. Alginate lyase activity was assessed by well diffusion method. 0.1 ml aliquots of crude enzyme from the wild type and mutant strains were poured in the wells and kept overnight for diffusion along with medium blank as a control. Plates were then

flooded with Gram's iodine solution, zone of hydrolysis was observed (14, 15).

# **Alginate Extraction**

1 mL of EDTA sodium salt solution (0.5M) and 0.5 mL of NaCl solution (5.0M), was added to the fermented broth, then centrifuged at 18000 rpm at 20°C for 30 minutes to separate the bacterial cell mass and substrate residues. Supernatant was then cooled by keeping in ice bath and three volumes of ice cold isopropanol wasadded. The mixture was left overnight at 4°C. Further it was centrifugation was done at 18000 rpm at 4°C for 30 min to precipitate alginate. The residue obtained was then dissolved in sterile distilled water, centrifuged, and finally the precipitates were dried at 80°C for 24 hours. Weights of the dried estimates were obtained gravimetrically (16). Precipitates of alginic acid were moistened with sterile distilled water and sodium carbonate was added to enhance the dissolution of alginate. Chilled ethanol was added to coagulate sodium alginate.

### **HPLC Analysis**


The coagulated sample was further analyzed by HPLC method (17, 18). Sample was analyzed on Shimadzu Class – VPV 6.14 SP1 system at 30°C using Optimac C18 (150 x 4.6 mm) column. Mobile phase – 40 mM K<sub>2</sub>HPO<sub>4</sub>, pH was adjusted to 6.0 by NaOH. Selected detector wavelength – 200 nm, injection volume – 20  $\mu$ l, alginate sample concentration – 1mg/ml (19).

## **Statistical Analysis**


The data obtained in triplicates was analyzed using MS Excel and by One-Way ANOVA tool (20).

# **Results and Discussion**


Optimization of temperature, pH, incubation duration (hours), agitation rate (rpm), inoculum age (hours), inoculum level (%) for production of alginate. Analysis of purified alginate by HPLC.

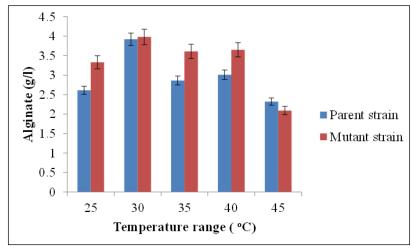


**Figure (1a):** Effect of Temperature on Production of Alginate (g/l). Each Bar Denotes Mean Value Based on Three Replicates and Y Error Bars are for Standard Error of Mean

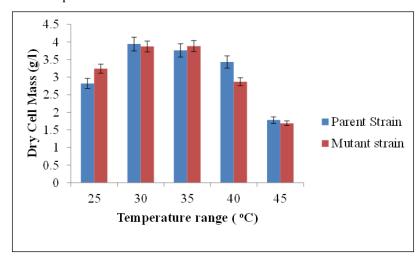


**Figure (1b):** Effect of Temperature on Dry Cell Mass (g/l). Each Bar Denotes Mean Value Based on Three Replicates and Y Error Bars are for Standard Error of Mean

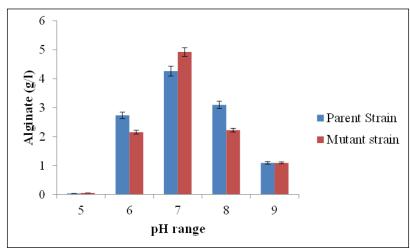


**Figure (2a):** Effect of pH on Production of Alginate (g/l). Each Bar Denotes Mean Value Based on Three Replicates and Y Error Bars are for Standard Error of Mean

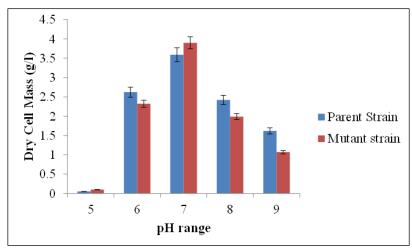


**Figure (2b):** Effect of pH on Dry Cell Mass (g/l). Each Bar Denotes Mean Value Based on Three Replicates and Y Error Bars are for Standard Error of Mean

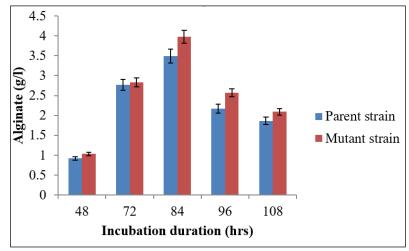


**Figure (3a):** Effect of Incubation duration on Production of Alginate (g/l). Each Bar Denotes Mean Value Based on Three Replicates and Y Error Bars are for Standard Error of Mean

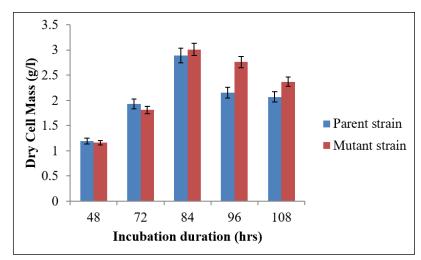


**Figure (3b):** Effect of Incubation duration on Dry Cell Mass (g/l). Each Bar Denotes Mean Value Based on Three Replicates and Y Error Bars are for Standard Error of Mean

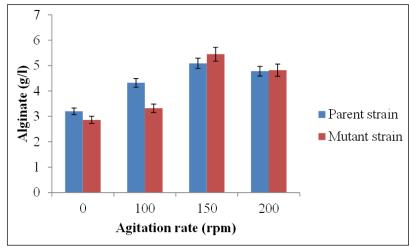


**Figure (4a):** Effect of Agitation Rate (Rpm) on Production of Alginate (G/L). Each Bar Denotes Mean Value Based on Three Replicates and Y Error Bars are for Standard Error of Mean

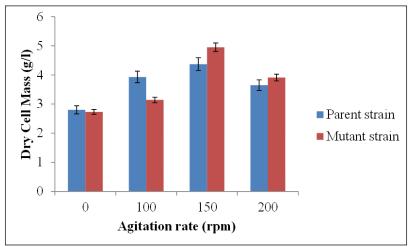


**Figure (4b):** Effect of Agitation Rate (rpm) on Dry Cell Mass (g/l). Each Bar Denotes Mean Value Based on Three Replicates and Y Error Bars are for Standard Error of Mean

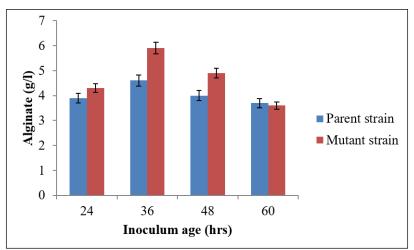


**Figure (5a):** Effect of Inoculum Age on Production of Alginate (g/l). Each Bar Denotes Mean Value Based on Three Replicates and Y Error Bars are for Standard Error of Mean

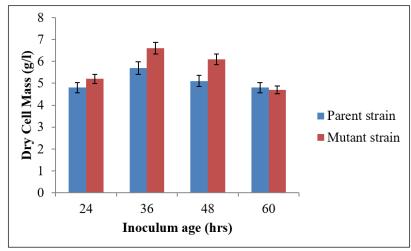

**Figure (5b):** Effect of Inoculum Age (Hrs) on Dry Cell Mass (g/l). Each Bar Denotes Mean Value Based on Three Replicates and Y Error Bars are for Standard Error of Mean

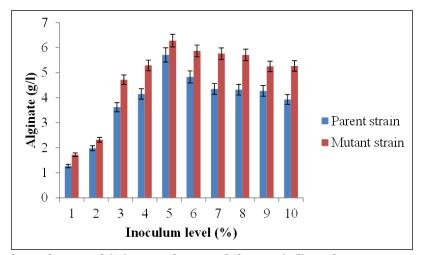

**Figure (6a):** Effect of Inoculum Level (%) on Production of Alginate (g/l). Each Bar Denotes Mean Value Based on Three Replicates and Y Error Bars are for Standard Error of Mean

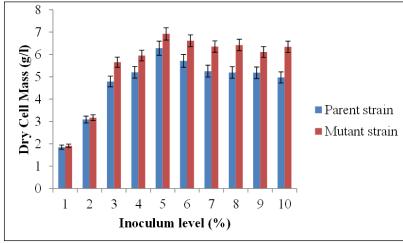

**Figure (6b):** Effect of Inoculum Level (%) on Dry Cell Mass (g/l). Each Bar Denotes Mean Value Based on Three Replicates and Y Error Bars are for Standard Error of Mean

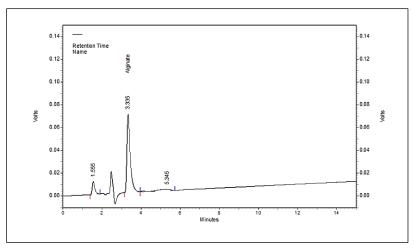


Figure 7: HPLC Chromatogram

Industrial by-products can be utilized for production of alginate (18). In the present study the optimum fermentation temperature 30°C was found to be suitable for maximum alginate production 3.92 g/L (PS) and 3.98g/L (MS) with the corresponding dry cell mass (DCM) as 3.76 g/L (PS) and 3.88 g/L (MS)as shown in Figure 1a and 1b. These results are supported by investigators (12, 13), as they also reported the same optimum incubation temperature for maximum biopolymer production. pH 7.0 was found as optimum with the production of alginate as 4.26 g/L (PS) and 4.92 g/L (MS) with the corresponding dry cell mass (DCM) as  $3.59 \,\mathrm{g/L}$  (PS) and  $3.90 \,\mathrm{g/L}$  (MS) as shown in Figure 2a and 2b. Same pH has been reported as optimum for exo-polysaccharide production by Azotobacter vinelandii in various studies (12, 13). As the pH increased beyond the optimum level, it resulted in the reduction of available energy for biopolymer synthesis thus decreasing the yield of alginate (21). The optimization of incubation period for alginate production was investigated. Higher concentration of alginate was observed at 84 hours, 3.92 g/L (PS) and 3.98 g/L (MS) with the corresponding dry cell mass (DCM) as 3.76 g/L (PS) and 3.88 g/L (MS) as shown in Figure 3a and 3b. With further increase in time, reduction in product formation was observed due to exhaustion of nutrients. Optimum agitation rate was at 150 rpm, with quantity of alginate 5.09 g/L (PS) and 5.45 g/L (MS) with the corresponding dry cell mass (DCM) as 4.37 g/L (PS) and 4.95 g/L (MS)(Figure 4a and 4b). These results gets correlated with the observations of other researchers (12, 22), they observed increased alginate synthesis at 200 rpm in shake flask studies. The suitable inoculum age was found to be 36 hours with quantity of alginate

as 4.6 g/L (PS) and 5.9 g/L (MS) with the corresponding dry cell mass (DCM) as 5.7 g/L (PS) and 6.6 g/L (MS) (Figure 5a and 5b). In the present study, medium containing molasses (2%) and peptone (0.5%) under various optimized parameters and the inoculum size 5% was found to give significantly (P≤ 0.05) higher yield of alginate 5.71 g/L (PS) and 6.28 g/L (MS) with the corresponding dry cell mass (DCM) as 6.28 g/L (PS) and 6.92 g/L (MS) as shown in Figure 6a and 6b. 2% inoculum size was reported to be optimum (13). Another researcher reported maximum yield with carbon sources sucrose (1%) and beet molasses (2%) (22). A. vinelandii can efficiently utilize molasses as the substrate and release the product in shorter time duration. Zone of hydrolysis by plate assay for alginate lyase activity was found to be 14 mm and 11 mm for the parent strain and the improved strain respectively, which contributes in enhanced yield of the product (23-25). The quantitative estimation of alginate was done by HPLC using sodium alginate standard of Sigma - Aldrich. The HPLC chromatogram indicated the peak of purified alginate at retention time of 3.335 minutes with percentage purity of 81.22% as compared to standard as shown in Figure 7. Confirmation by HPLC is one of the best method and the results of extracted alginate in comparison to the standard seaweed alginate are in accordance with other investigators (26-28).

# Conclusion

In this research work pre-treated sugar cane molasses as a cheap carbon source was used which can reduce the cost of biosynthesis of alginate and can be economically feasible. Organic nitrogen source like peptone favors the growth rate of the

microorganism and the yield of the product. The optimized parameters contributes significantly in the yield obtained. Screening for alginate lyases during fermentation must be an essential step in such research work, either a plate assay or spectrophotometric assay of enzymatic reaction. Purification of the product at the onset of secretion of enzymes or inhibition of alginate lyases is highly recommended. It is suggested to monitor DOT as it has been reported by the researchers to be contributing in obtaining the maximum yield of alginate with high molecular weight.

#### **Abbreviations**

PS: Parent strain, MS: Mutant strain, DCM: Dry Cell Mass, DOT: Dissolved Oxygen Tension, HPLC: High Performance Liquid chromatography, *A. vinelandii: Azotobacter vinelandii*.

## Acknowledgement

The authors express gratitude to the Principal, Maulana Azad College of Arts, Science and Commerce, Aurangabad for providing the facilities during the research.

#### **Author Contributions**

Zarina Shaikh: Conceptualized the study, collected the literature and methodology, performed the experiments, and wrote the manuscript, Mohd. Shakir: provided valuable guidance and edited the manuscript.

#### **Conflict of Interest**

The authors hereby declare no conflicts of interest regarding the publication of the manuscript.

# **Ethics Approval**

Not applicable.

# **Funding**

Not applicable.

#### References

- Noar JD and Bruno-Bárcena JM. Azotobacter vinelandii: the source of 100 years of discoveries and many more to come. Microbiology. 2018 Apr;164(4):421-36.
- Nivens DE, Ohman DE, Williams J, Franklin MJ. Role of alginate and its O acetylation in formation of *Pseudomonas aeruginosa* microcolonies and biofilms. Journal of bacteriology. 2001 Feb 1;183(3):1047-57.
- 3. Franklin MJ, Chitnis CE, Gacesa P, Sonesson A, White DC, Ohman DE. *Pseudomonas aeruginosa* AlgG is a polymer level alginate C5-mannuronan epimerase. Journal of bacteriology. 1994 Apr;176(7):1821-30.
- 4. Schiller NL, Monday SR, Boyd CM, Keen NT, Ohman DE. Characterization of the Pseudomonas aeruginosa alginate lyase gene (algL): cloning, sequencing, and

- expression in *Escherichia coli*. Journal of bacteriology. 1993 Aug; 175(15): 4780-9.
- 5. Lee KY and Mooney DJ. Alginate: properties and biomedical applications. Progress in polymer science. 2012 Jan 1;37(1):106-26.
- Dudun AA, Akoulina EA, Voinova VV, Makhina TK, Myshkina VL, Zhuikov VA, Bonartsev AP, Bonartseva GA. Biosynthesis of alginate and poly (3hydroxybutyrate) by the bacterial strain *Azotobacter* agile 12. Applied biochemistry and microbiology. 2019 Nov:55:654-9.
- Tøndervik A, Aarstad OA, Aune R, Maleki S, Rye PD, Dessen A, Skjåk-Bræk G, Sletta H. Exploiting mannuronan C-5 epimerases in commercial alginate production. Marine drugs. 2020 Nov 18;18(11):565.
- Galindo E, Peña C, Núñez C, Segura D, Espín G. Molecular and bioengineering strategies to improve alginate and polydydroxyalkanoate production by Azotobacter vinelandii. Microbial cell factories. 2007 Dec;6:1-6.
- Peña C, Castillo T, Núñez C, Segura D. Bioprocess design: fermentation strategies for improving the production of alginate and poly-β-hydroxyalkanoates (PHAs) by *Azotobacter vinelandii*. Rijeka, Croatia: INTECH-Open Access Publisher.2011:217-42. DOI: 10.5772/20393
- 10. Dudun AA, Akoulina EA, Zhuikov VA, Makhina TK, Voinova VV, Belishev NV, Khaydapova DD, Shaitan KV, Bonartseva GA, Bonartsev AP. Competitive biosynthesis of bacterial alginate using *Azotobacter vinelandii* 12 for tissue engineering applications. Polymers. 2021 Dec 30;14(1):131.
- 11. Wang J, Liu S, Huang J, Ren K, Zhu Y, Yang S. Alginate: Microbial production, functionalization, and biomedical applications. International journal of biological macromolecules. 2023 Jul 1;242:125048.
- 12. Butt ZA and Qadeer MA. Alginate production by a mutant strain of *Azotobacter vinelandii* using shake flask fermentation. Pakistan Journal of Botany. 2011 Apr 15;43(2):1053-1067.
- 13. Vermani MV, Kelkar SM, Kamat MY. Studies in polysaccharide production and growth of *Azotobacter vinelandii* MTCC 2459, a plant rhizosphere isolate. Letters in applied microbiology. 1997 May;24(5):379-83.
- 14. Gacesa P, Wusteman FS. Plate assay for simultaneous detection of alginate lyases and determination of substrate specificity. Applied and environmental microbiology. 1990 Jul;56(7):2265-7.
- 15. Sawant SS, Kumar KV, Balaram V, Rao DS, Rao KS, Tiwari RP. Geochemistry and genesis of craton-derived sediments from active continental margins: insights from the Mizoram Foreland Basin, NE India. Chemical Geology. 2017 Oct 20;470:13-32.
- 16. Knutson CA and Jeanes A. A new modification of the carbazole analysis: application to heteropolysaccharides. Analytical biochemistry. 1968 Sep 1;24(3):470-81.
- 17. Awad H and Aboul-Enein HY. A validated HPLC assay method for the determination of sodium alginate in pharmaceutical formulations. Journal of chromatographic science. 2013 Mar 1;51(3):208-14.
- 18. Saeed S, Hashmi AS, Ikram-ul-Haq IU, Tayyab M, Awan AR, Anjum AA, Firyal S. Bioconversion of agricultural by-products to alginate by *Azotobacter vinelandii* and physico-chemical optimization for

- hyper-production. The Journal of Animal & Plant Sciences. 2016; 26(5):1516-1521.
- 19. Rele RV and Warkar CB. Reversed phase high pressure liquid chromatographic technique for determination of sodium alginate from oral suspension. Int J Pharm Tech Res. 2010;2:1634-8.
- 20. Correia-Sousa J, Tabaio AM, Silva A, Pereira T, Sampaio-Maia B, Vasconcelos M. The effect of water and sodium hypochlorite disinfection on alginate impressions. Revista Portuguesa de Estomatologia, Medicina Dentária e Cirurgia Maxilofacial. 2013; 54(1):8-12.
- 21. Pandurangan G, Jyothi S, Karunakaran T, David KJ. Small scale production and characterization of alginate from *Azotobacter chroococcum* using different substrates under various stress conditions. Int J ApplBiol Pharm Technol. 2012;3:40-5.
- 22. Emtiazia G, Ethemadifara Z, Habibib MH. Production of extra-cellular polymer in Azotobacter and biosorption of metal by exopolymer. African Journal of Biotechnology. 2004;3(6):330-3.
- 23. Cheng D, Jiang C, Xu J, Liu Z, Mao X. Characteristics and applications of alginate lyases: A review. International Journal of Biological Macromolecules. 2020 Dec 1;164:1304-20.
- 24. Tkalec G, Kranvogl R, Uzunalić AP, Knez Ž, Novak Z. Optimization of critical parameters during alginate aerogels' production. Journal of Non-Crystalline Solids. 2016 Jul 1;443:112-7.
- 25. Wang M, Chen L, Zhang Z, Wang X, Qin S, Yan P. Screening of alginate lyase-excreting microorganisms from the surface of brown algae. AMB Express. 2017 Dec;7:1-9.
- 26. Saad MH, Sidkey NM, El-Fakharany EM. Identification and statistical optimization of a novel alginate polymer extracted from newly isolated Synechocystis algini MNE ON864447 with antibacterial activity. Microbial Cell Factories. 2023 Nov 7;22(1):229.
- 27. Owlia P, Souri E, Behzadian-Nejad Q. Novel high-performance liquid chromatography method for detection of alginate in *Pseudomonas aeruginosa*. Iranian Journal of Pathology. 2007;2(3):104-108.
- 28. Shroff P, Parikh S, Smt SM. Production and characterization of alginate extracted from *Paenibacillus riograndensis*. Research Journal of Life Sciences, Bioinformatics, Pharmaceutical and Chemical Sciences, 2018; 4(6):560-75.